

Soft Matter

rsc.li/soft-matter-journal



ISSN 1744-6848



PAPER

C. Patrick Royall *et al.*
Coupling between criticality and gelation in “sticky” spheres: a structural analysis



Cite this: *Soft Matter*, 2018, 14, 5554

Coupling between criticality and gelation in “sticky” spheres: a structural analysis†

David Richard,^a James Hallett,^{ib} Thomas Speck^{ib} and C. Patrick Royall^{ib} *bcd

We combine experiments and simulations to study the link between criticality and gelation in sticky spheres. We employ confocal microscopy to image colloid–polymer mixtures and Monte Carlo simulations of the square-well (SW) potential as a reference model. To this end, we map our experimental samples onto the SW model. We find an excellent structural agreement between experiments and simulations, both for locally favored structures at the single particle level and large-scale fluctuations at criticality. We follow in detail the rapid structural change in the critical fluid when approaching the gas–liquid binodal and highlight the role of critical density fluctuations for this structural crossover. Our results link the arrested spinodal decomposition to long-lived energetically favored structures, which grow even away from the binodal due to the critical scaling of the bulk correlation length and static susceptibility.

Received 26th February 2018,
Accepted 9th May 2018

DOI: 10.1039/c8sm00389k

rsc.li/soft-matter-journal

1. Introduction

Understanding how an amorphous system becomes dynamically arrested upon compression or cooling is a long-standing challenge in statistical physics. Such amorphous solids encompass states of matter such as glasses, films, plastics, and gels, among others. Despite the fact that these systems are of technological importance and have received a lot of attention in the literature,^{1,2} the microscopic mechanism responsible for macroscopic arrest remains elusive. For instance, the question whether the glass transition can be explained in the context of a thermodynamic or structural phase transition is still debated.^{3–7} Interestingly, gels, in contrast to glasses, can have very sparse spatial structural arrangements, often described by a percolating network of bonded particles whose degree of dilution can in principle be unbounded.^{8,9} These networks can result from cross-linking polymer chains or from physical bonds. The latter are caused, *e.g.*, by depletion attractions¹⁰ and for some time have served as a well-controlled model system to study glasses and gels.^{10–18}

Upon decreasing the range of attraction between particles, the gas–liquid coexistence becomes metastable with respect to fluid–solid coexistence, with a metastable critical point.^{19,20} In the limit where the attraction range becomes smaller

than roughly 10% of the diameter of the particles, the shape of the attractive part of the pair-wise potential becomes irrelevant.^{20,21} This gave rise to the extended law of corresponding states,²¹ which can also explain some aspects of the phase behavior of protein solutions.^{22–24} Experimentally, such a short-ranged attraction can be probed using colloid–polymer mixtures,¹⁰ so-called “sticky” spheres. Here, the polymers play the role of depletants for the large colloidal particles, where the radius of gyration of the polymer chains sets the range of attraction.

In the context of understanding the gelation of particles with short-ranged attraction, much work has been done during the last 20 years.^{8,13,16,25–34} Several scenarios have been proposed, including diffusion-limited cluster aggregation,^{35,36} phase separation,^{8,29} and percolation,^{26,37,38} and these can couple in different regions of the phase diagram.⁹ Some of this work links the gelation to an arrested spinodal decomposition^{8,16,29,39} and thus, a direct consequence of the underlying gas–liquid coexistence. A possible microscopic mechanism for the arrest was proposed with the presence, at gelation, of clusters that minimise the local potential energy.¹⁶ Furthermore, it has been shown that gelation in sticky spheres offers a clear dynamical signature in comparison with a hard-sphere glass, where authors found a quasi-discontinuous increase in the relaxation time of the fluid for various packing fractions.³⁴ These dynamical transitions were found to be located at the gas–liquid binodal, even for a very dense gel, with a packing fraction exceeding the freezing point of the hard-sphere fluid.³⁴ Another study has suggested that the gelation line is located before the phase separation and extends at higher densities toward the location of the attractive glass.⁴⁰ A more recent numerical study³⁷ of the adhesive hard-sphere model^{41,42} has linked the experimental gelation line to the mean-field rigidity

^a Institut für Physik, Johannes Gutenberg-Universität Mainz, Staudingerweg 7-9, 55128 Mainz, Germany

^b HH Wills Physics Laboratory, Tyndall Avenue, Bristol BS8 1TL, UK.
E-mail: chcpr@bristol.ac.uk

^c School of Chemistry, University of Bristol, Cantock's Close, Bristol, UK

^d Centre for Nanoscience and Quantum Information, Tyndall Avenue, Bristol, UK

† Electronic supplementary information (ESI) available. See DOI: 10.1039/c8sm00389k

transition introduced by He and Thorpe⁴³ in the context of random networks. More recently, a connection between directed percolation⁴⁴ as an equilibrium pre-structural transition to gelation has been proposed.³⁸

The suggested relationship between the liquid-gas phase separation line^{29,34,39} and gelation implies that critical fluctuations may influence the gelation process in the vicinity of the critical isochore. While criticality has been studied in colloid-polymer systems,^{45,46} this work has tended to focus on systems where the interaction range is long enough that the system exhibits a stable colloidal liquid phase. In colloid-polymer mixtures, this corresponds to a polymer-colloid size ratio of around 0.3.^{10,47} For such systems, the colloidal liquid is not dense enough to arrest, and gelation is only achieved upon quenching with a much stronger attraction strength than that required for criticality.⁴⁸ However, in the sticky sphere limit, immediately upon quenching through the binodal, the density of the colloidal “liquid” is sufficient that the system undergoes dynamical arrest.³⁴ Under these circumstances, gelation may couple to critical fluctuations and this forms the subject of our study.

II. Methods

A. Experiments

We employ confocal microscopy and particle tracking to resolve the positions of the colloidal particles. Colloid-polymer mixtures are composed of polystyrene (PS) polymer chains and sterically stabilized polymethyl methacrylate (PMMA) spheres with diameter $\sigma_{\text{SEM}} = 2950$ nm and polydispersity $\Delta = 5\%$, determined *via* scanning electronic microscopy (SEM). We use rhodamine as a fluorescent label. Polystyrene has a molecular weight $M_w = 1.3 \times 10^6$ corresponding to an effective radius of gyration $R_g = 35$ nm under θ conditions. We use a solvent mixture of *cis*-decalin and cyclohexyl bromide which is density and refractive index-matched. We additionally screen electrostatic interactions using 4 mmol of tetrabutylammonium bromide salt. From previous work,¹⁷ we estimate $R_g \simeq 50$ nm at room temperature. This leads to a polymer-colloid size ratio $q \simeq 0.03$ approaching the sticky sphere limit. Samples are first shear-melted. We then seal each sample into a borosilicate glass capillary with epoxy resin. We let the samples equilibrate for 30 minutes before imaging. From previous work, this time it is estimated to correspond to more than 200 Brownian times.³⁴

The samples are imaged by confocal microscopy using a Leica SP8. We image different parts of the suspension at least 15 μm from the wall. To extract the colloidal particle positions, we employ three-dimensional particle tracking using the difference in the Gaussian method. This tracking is performed using the package “Colloid” developed by Leocmach *et al.*⁴⁹ From the tracking we estimate the sample packing fraction as $\phi \simeq \pi N \sigma^3 / (6V)$, with N is the number of tracked particles and V is the volume of the sample. It is well known that sterically stabilized PMMA colloidal particles can exhibit swelling and unscreened electrostatic interactions,^{50,51} which can lead to

intrinsic softness modeled by an effective diameter $\sigma > \sigma_{\text{SEM}}$. To estimate σ under our experimental conditions, we apply a method similar to the one used in ref. 52. In this study, the authors matched the pair correlation function $g(r)$ of dense hard spheres with the known Percus-Yevick expression by varying the effective diameter σ . In our work, we extend this mapping with matching the $g(r)$ of the colloid-polymer mixture with an attractive square-well fluid, which we adopt throughout this study as a reference system for our mixtures. In addition, our mapping allows us to determine the systematic tracking errors of the colloidal positions, responsible for the broadness of $g(r)$ at contact.⁴⁶ More details can be found in Appendix A. We find $\sigma = 3100$ nm, which corresponds to an effective diameter that is $\sim 5\%$ larger than for the SEM estimation.

B. Computer simulations

We study the behavior of the square-well (SW) model serving as a reference model for our colloid-polymer mixtures. We perform standard Monte Carlo simulations in the *NVT* ensemble employing local moves. The system is composed of $N = 5000$ particles with diameters drawn from a Gaussian distribution with polydispersity $\Delta = 5\%$. The interaction potential between two particles i and j is

$$V(r) = \begin{cases} \infty & \text{if } r \leq \sigma_{ij} \\ -V_{\text{SW}} & \text{if } \sigma_{ij} < r < \sigma_{ij} + \delta, \\ 0 & \text{if } r \geq \sigma_{ij} + \delta \end{cases}, \quad (1)$$

where $\sigma_{ij} = (\sigma_i + \sigma_j)/2$, with σ_i and σ_j being the diameters of particles i and j respectively. The attraction range δ is set by the polymers and fixed to 0.03σ and is independent of σ_{ij} . If not mentioned otherwise, simulations are performed in a cubic box. Additionally, we use a slab geometry to compute the coexistence packing fraction between the gas and liquid phases with box lengths: $L_x = L_y = L_z/2$. Initial configurations are randomly drawn and any overlap between particles is removed using the algorithm by Clarke and Wiley.⁵³ We determine the binodal by fitting the density profile along the gas-liquid coexistence through

$$\phi(z) = \frac{\phi_l - \phi_g}{2} + \frac{\phi_l - \phi_g}{2} \tanh\left(\frac{z - z_0}{2w}\right). \quad (2)$$

Here, ϕ_g and ϕ_l denote the gas and liquid coexistence packing fractions, and z_0 and w denote the interface position and width, respectively. Since for this polydispersity the liquid is still metastable with respect to the crystal, we check that all liquid slabs remained in the liquid phase. All distances and energies are expressed in units of σ and $k_B T$, with k_B being the Boltzmann constant. Throughout, we denote the dimensionless attraction strength by $V = V_{\text{SW}}/k_B T$.

C. Mapping procedure

The attraction strength between colloidal particles is controlled by the polymer concentration c_p . However, it is challenging to determine c_p precisely enough to map it directly. Instead, we map every sample individually through matching the experimentally

measured total correlation function $h_{\text{exp}}(r) = g_{\text{exp}}(r) - 1$ and the distribution $P_{\text{exp}}(n)$ of bond numbers n to the SW fluid,^{29,46} yielding an effective attraction strength V for every experimental sample.

Specifically, we compute $rh_{\text{sim}}(r)$ and $P_{\text{sim}}(n)$ on a grid in the (ϕ, V) plane around the critical point. We evaluate $P(n)$ by constructing a bond network using a Voronoi decomposition considering only direct Voronoi neighbors^{54,55} with the bond distance cut-off r_c set to 1.5σ . Following the work of Largo *et al.*, we estimate the location of the critical point to be at $\phi_c \simeq 0.275$ and $V_c \simeq 3.22$ for zero polydispersity.²⁰ We shall show later on that this value is very close to the critical point of our model with $\Delta = 5\%$. We use packing fractions ranging from $\phi = 0.05$ to 0.5 with an interval $\Delta\phi = 0.025$ and V values ranging from 0 to 4 with $\Delta V = 0.2$ for $0 < V < 2$ and $\Delta V = 0.1$ for $2 < V < 4$. Overall, we end up with a grid of 608 state points. Beyond $V \simeq 3.2$, the fluid crosses the binodal and starts to form a gel. Thus, structural observables such as $h(r)$ and $P(n)$ might evolve due to aging. We fix for every state point an MC relaxation time of 10^6 steps before we compute any observables. Another 10^6 steps is used to compute observables. We then pick for each sample the two numerical packing fractions ϕ_- and ϕ_+ , which encompass our sample density. We then compute for each V value h_{sim} and P_{sim} as a linear combination of ϕ_- and ϕ_+ . We finally compute as a “goodness” parameter for our matching procedure the least squares

$$\chi_h^2 = \sum_i [r_i(h_{\text{exp}}(r_i) - h_{\text{sim}}(r_i))]^2 \quad (3)$$

and

$$\chi_P^2 = \sum_i [P_{\text{exp}}(n_i) - P_{\text{sim}}(n_i)]^2. \quad (4)$$

In practice, χ_h^2 is computed for $r < 4\sigma$, while an additional Gaussian ($\Delta = 5\%$) noise is added on numerical positions to mimic particle-tracking errors⁴⁶ (see Appendix A). The global minima of χ_h^2 and χ_P^2 give us two independent evaluations of V_{exp} . We then assign for each sample the mean of those two, $V_{\text{exp}} = (V_h + V_P)/2$, whereas $|V_h - V_P|/2$ serves as an estimation for errors.

In Fig. 1(a) and (b), we present χ_h^2 and χ_P^2 as a function of V for three samples picked along the critical isochore. From a hard sphere fluid (gray curves) to the gel (orange curves), we always observe a global minimum for χ^2 and find a good agreement between V_h and V_P . Results of the SW model are shown in Fig. 1(c and d) and compared to experimental data. The correspondence between experiments and simulations is excellent, and we observe only small discrepancies in the bond-number distribution for the gel sample for small bond numbers n (see Fig. 1(d)). Since the fluid is ergodic, the mapping to the SW fluid should be robust (as indeed it is). In contrast, the gel is non-ergodic and thus the correspondence would depend on the dynamics and history.⁷⁰ Hence, these deviations are not surprising since we do not include the effect of aging in our mapping method.

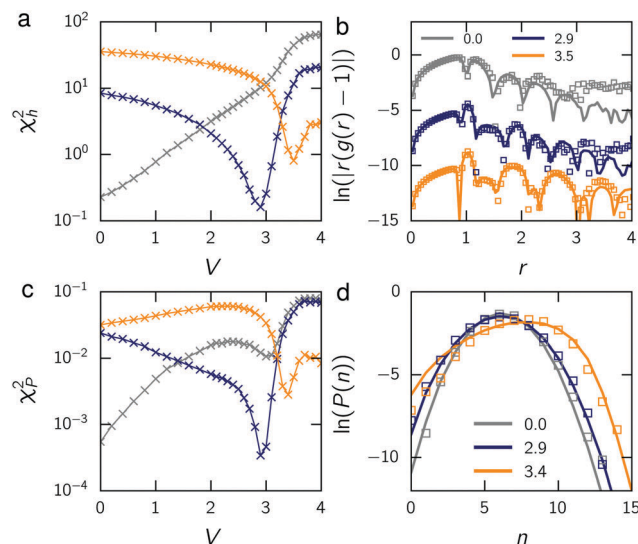


Fig. 1 Mapping onto the square-well model. (a and b) Evolution of the least squares χ^2 as a function of the attraction strength V for the total correlation function $rh(r)$ (a) and bond distribution $P(n)$ (b) of three samples. (c and d) Comparison of $rh(r)$ (c) and $P(n)$ (d) of the experimental samples (empty symbols) with the SW model for matched V (lines). The color code distinguishes a hard-sphere fluid (gray) from a critical (blue) and gel (orange) sample.

III. Results

A. Phase diagram

We start by discussing the phase behavior of our system as shown in Fig. 2. We choose to present our data in the ϕ - V plane. The gas-liquid binodal of our reference system is indicated by the black solid line. The location of the critical point is indicated by a black star and was determined *via* the block distribution function method,⁵⁶ we shall come back to this point later. From our mapping procedure, we can place each sample at a given ϕ and V . We distinguish an ergodic fluid in contrast to a gel by respectively blue and orange square symbols. We also indicate the samples without polymers, *i.e.* hard spheres, in gray. The typical gel sample shows a clear dynamical arrest with a relaxation time beyond $100\tau_B$ (ESI,† Video) with τ_B being the Brownian time. This is consistent with a previous dynamical experimental study for a very similar system.³⁴

The main observation here is that arrested samples are lying close to the binodal for a wide range of densities ($0.1 < \phi < 0.4$). That is to say, all samples which are gels always map onto state points of the reference system which are on or above the binodal. This means that the radial distribution function and bond distribution of a gel sample never correspond to an ergodic fluid. This is in agreement with previous numerical and experimental studies, which associate the gelation with the location of the spinodal and thus a direct consequence of the equilibrium properties of the gas-liquid coexistence.^{8,16,29,34} For short-ranged attractive systems, the binodal and spinodal are located very close together, such that in experiments it is hard to distinguish them.³⁴ The highest attraction strength at which the sample remains ergodic is found at $V \simeq 2.9$. Additionally, in Fig. 2, we

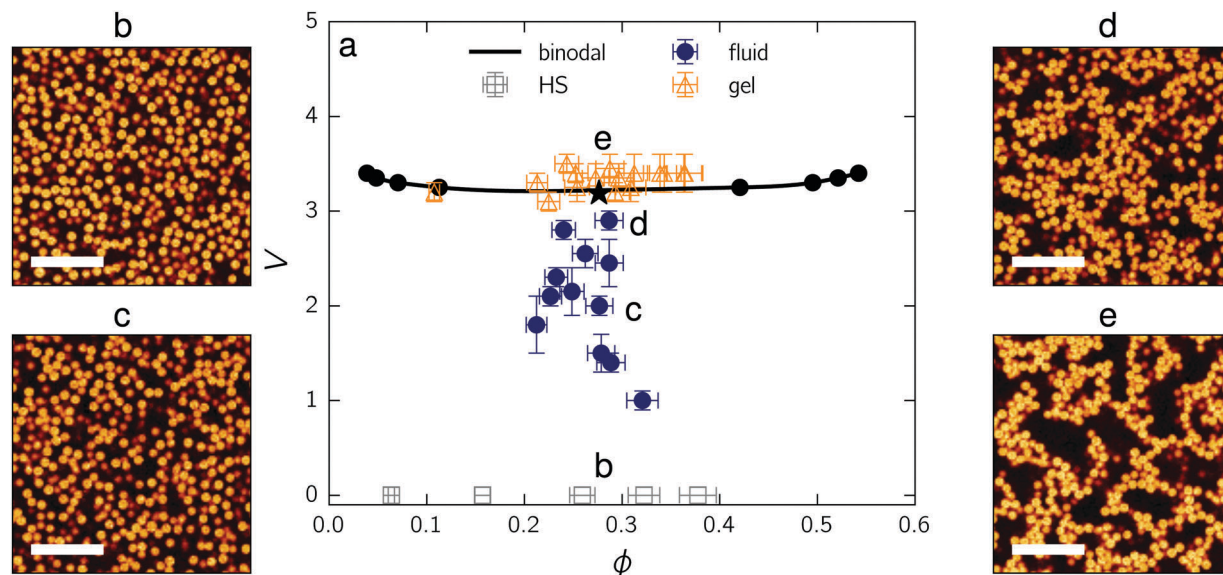


Fig. 2 Phase diagram. (a) Phase diagram of the square-well with $\delta = 3\%$ and polydispersity $\Delta = 5\%$. Black points indicate the gas–liquid coexistence and the black star indicates the critical point. The black solid line is a guide to the eye for the two-phase boundary. Gray, blue, and orange squares are, respectively, hard-sphere fluid, colloid–polymer mixtures, and arrested gel samples. Confocal images are displayed in a–d: (b) hard-sphere fluid without polymers ($V \approx 0.0$); (c) equilibrium fluid ($V \approx 2.0$); (d) fluid close to criticality ($V \approx 2.9$) and (e) gel phase ($V \approx 3.2$). The scale bars correspond to $20\ \mu\text{m}$.

show the images using confocal microscopy along the critical isochore $\phi \approx \phi_c$. We observe a rather continuous change of structural behavior from hard-sphere fluid to gel. At $V = 0$ (Fig. 2(b)), the spatial distribution of colloids is homogeneous at length scales larger than the particle size. When increasing the concentration of polymers, *i.e.* increasing V , clusters start to form with lower densities in between (Fig. 2(c and d)). Finally, the suspension shows an arrested spinodal decomposition, which is revealed in Fig. 2(e) by large assemblies rich in colloidal particles and depleted zones without any particles.

B. Critical density fluctuations

In Section IIIA, we have shown that the gelation line is located close to the binodal and that dense domains of colloidal particles grow progressively as a function of polymer concentration. We now demonstrate how this change in behavior can be directly linked to the fluctuations present in the context of criticality. To quantify the spatial evolution of the density, we use the block distribution function method,⁵⁶ which provides the location of the critical point V_c ⁵⁷ and to some extent the isothermal susceptibility χ of the fluid.^{58,59} The procedure is as follows: We divide our system into a series of cubic subcells of dimension $l = L/b$, with b being an integer. The global density is defined as $\bar{\rho} = \frac{1}{n_b} \sum_i \rho_i$, where $n_b = b^3$ is the number of subcells and ρ_i is the local density in the subcell i . We then extract the second and forth moments of density $\langle m_2 \rangle$ and $\langle m_4 \rangle$ computed as $\langle m_x \rangle_l = \frac{1}{n_b} \sum_i (\rho_i - \bar{\rho})^x$. We can finally define the Binder cumulant through

$$U_l = \frac{\langle m_4 \rangle_l}{\langle m_2 \rangle_l^2} \quad (5)$$

One of the main properties of U_l is its size invariance with respect to l at the critical point.⁵⁶ This allows us to determine unambiguously and accurately the critical attraction strength V_c in computer simulations. In more detail, we compute U_l for various attraction strengths V and subcell lengths l . To this end, we sample U_l for each V values at a fixed packing fraction $\phi \approx \phi_c = 0.275$ using extra 10^8 MC steps. In Fig. 3, we show the evolution of U_l as a function of V . We observe a crossing for $V > 3$, which can be resolved more accurately as shown in the inset of Fig. 3(a). We find $V_c = 3.19(3)$ as the final value for the critical point, which is close to the value determined by Largo *et al.*²⁰ for zero polydispersity. Additionally, in Fig. 3, we show experimental results for U_l at a fixed subcell length, $l = 2\sigma$. Although the experimental data suffer from a lack of statistic in comparison with simulation data, we observe an overall good agreement. More precisely, gel samples indicated by orange squares are, within the errors, located either at the cumulant crossing or at larger attraction strengths.

The change in U_l is rationalized through a density distribution $P_l(\rho_i)$ that moves from a unimodal Gaussian shape, centered at $\rho_i = \bar{\rho}$, to a bimodal shape, where the two maxima of the distribution move progressively towards the coexistence densities ρ_- and ρ_+ . In Fig. 4 we show for both experiments and simulations the density distributions for subcells of length $l \approx 3\sigma$ (without reaching a truly bimodal distribution, presumably due to the vicinity to the critical point). To be consistent with the phase diagram given in Fig. 2, we choose to plot $P_l(\phi)$ instead of $P_l(\rho)$. We start with a hard-sphere sample (Fig. 4(a)) for which we observe a narrow distribution lacking low density ($\phi < 0.1$) and high density ($\phi > 0.5$) regions. The same behavior continues up to $V = 2$ (Fig. 4(b)). Upon further increasing V , we start to observe broader distributions with almost empty ($\phi < 0.1$) and

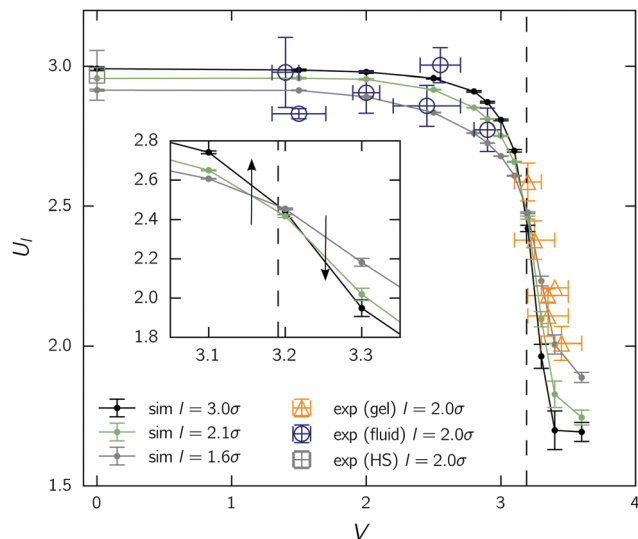


Fig. 3 Critical point. Evolution of the Binder cumulant U_l as a function of the attraction strength V for three values of l . Solid lines and open symbols indicate simulation and experimental data, respectively. The hard sphere, ergodic fluid, and arrested gel samples are distinguished by gray squares, blue circles and orange triangles respectively. Inset: Zoom into the crossing region for simulation data.

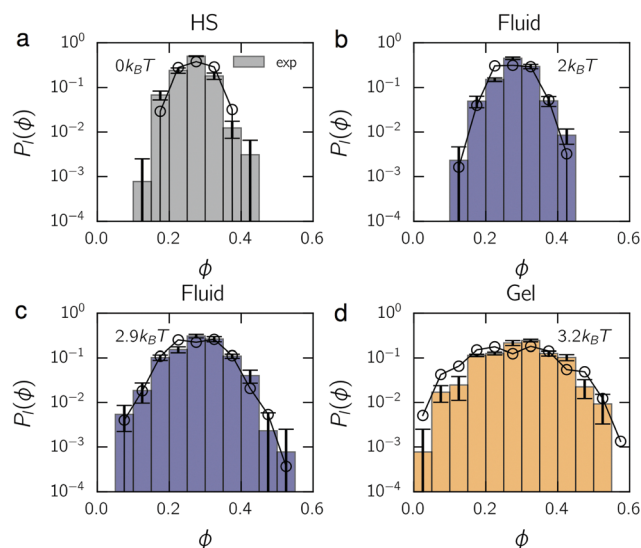


Fig. 4 Density fluctuations. Packing fraction distribution $P_l(\phi)$ for various samples and matched simulations along the critical path for the subcell length $l \approx 3\sigma$. Colored histograms and empty black circles are respectively experimental and simulation distributions. The effective attraction depth V for each sample is indicated in figures.

colloid-rich regions ($\phi > 0.5$). This can be clearly seen for our last ergodic sample at $V = 2.9$ (Fig. 4(c)). Interestingly, dense regions can reach packing fractions larger than the freezing point of a hard-sphere fluid. This explains why for non-polydisperse samples, one can expect a speed-up of crystallization around the critical point, where the dense regions arising from criticality will lower the nucleation barrier.^{17,19,60–62} Continuing to quench, the distribution becomes broader and non-Gaussian at $V = 3.2$, which

also corresponds to the location of our first gel sample. Surprisingly, we find that P_l^{exp} matches quite closely the equilibrated P_l^{sim} , indicating that aging effects are not pronounced. Finally, we can say that the overall behavior of $P_l(\phi)$ confirms quantitatively the observation made for confocal images in the previous section [Fig. 2(a–d)].

C. Fractal dimension, bulk correlation length, and bond distribution

We now turn to discuss the characteristic cluster shape and length scale formed by colloidal particles when quenched through criticality. We first compute the scattering intensity $I(q)$ as a function of the wave vector q from the Fourier transform of the confocal pixel map. In Fig. 5(a) we show a typical colloidal gel close to criticality and its associated Fourier spectrum in the inset. A radial average leads to $I(q)$ as shown in Fig. 5(b) for different samples along the critical isochore. Upon quenching, we observe a divergence of $I(q)$ for small q as a consequence of larger domains forming and diffusing light. Since the scattering intensity $I(q)$ is proportional to $P(q)S(q)$, where $P(q)$ is the form factor and $S(q)$ is the structure factor, we expect for $q > 2\pi/\sigma$ the scaling $I(q) \sim q^{-4}$, which is confirmed by the dashed line in Fig. 5(b). For small q , the scaling depends on the shape of the diffusing clusters through d_f and its fractal dimension. Previous small-angle neutron scattering (SANS) experiments have shown that the fractal dimension at the gelation is typically around $d_f \approx 1.7$,³¹ which is supported by particle-resolved experiments^{63,64} and simulation.⁹

We will discuss this point in detail later on. We can additionally extract $S(q)$ for the small wave vector from $S(q) = I(q)/(AP(q))$, where we evaluate $(AP(q))$ by fitting $I(q)$ for $q > 2\pi/\sigma$ by a polydisperse form factor and a prefactor A , as shown in the inset of Fig. 5(b). The resulting procedure is shown in Fig. 5(c) and directly compared to simulation data. We find an overall very good agreement between experimental data and simulations. The structure factor can then be used to extract an estimation of the bulk correlation length ξ through the Ornstein–Zernike scaling,

$$S(q) = \frac{S_0}{1 + (\xi q)^2}, \quad (6)$$

which holds close to criticality for small q . In Fig. 5(d), we plot the evolution of the fractal dimension d_f as a function of the attraction strength V . We find upon increasing V a progressive increase of d_f and saturation of gel samples at $d_f = 2.4$ – 2.5 . These values agree with fractal dimensions found for gel samples at low volume fractions and large attraction strength.⁹ At criticality, where gelation occurs, we find $d_f = 1.6$ – 1.7 , which is consistent with a previous SANS experimental study.³¹

As a measure for the distance to the critical point, we define the reduced attraction strength $\varepsilon = (V_c - V)/V$. In Fig. 5(e), we present the behavior of the bulk correlation length ξ as a function of ε . From the simulations, we find that ξ strongly increases as $\varepsilon \rightarrow 0$ and that this increase is well modelled by the Ising universality class with $\xi \sim \varepsilon^{-\nu}$ up to $\varepsilon \approx 0.2$, where in three dimensions $\nu \approx 0.63$. In contrast, for the experimental

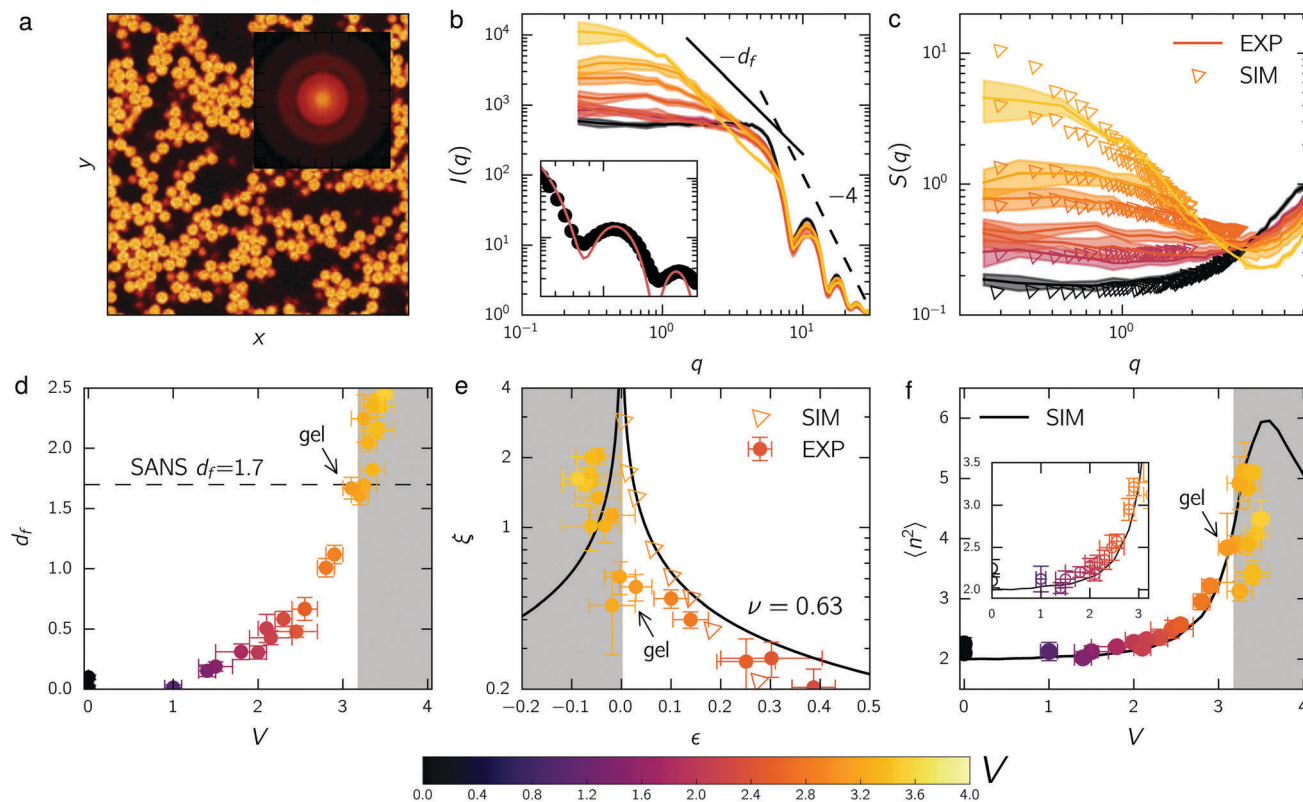


Fig. 5 Evolution of the fractal dimension, bulk correlation length, and bond distribution. (a) Confocal image of a gel close to criticality. The inset shows the associated scattering pattern. (b) Scattering intensity $I(q)$ as a function of the wave vector q for various samples along the critical isochore $\phi \simeq \phi_c$. Inset: Fit of the form factor to extract $S(q)$. (c) Structure factor $S(q)$ as a function of the wave vector q for the same samples. Solid lines are from simulation data at $\phi \simeq \phi_c$. (d) Evolution of the fractal dimension d_f as a function of the attraction strength V . The horizontal dashed line indicates the fractal dimension reported for SANS experiments.³¹ (e) Evolution of the bulk correlation length ξ as a function of the reduced attraction strength ϵ . Circles and triangles are experimental and simulation data, respectively. The black solid line indicates 3D Ising scaling with $\xi \sim \epsilon^{-0.63}$. (f) Variance $\langle n^2 \rangle$ of the bond distribution as a function of the attraction strength V . The solid black lines indicate the simulation data for the critical isochore. Inset: Ergodic fluids before gelation. All panels: arrows indicate the sample in which gelation occurred first and colors indicate attraction strength V .

data, the equilibrium fluids follow closely the simulation data until gelation occurs close to the binodal, whereby the system is arrested and therefore the correlation length does not increase beyond $\xi \approx 2\sigma$. This rather small spatial correlation is not in contradiction with confocal images of gels, where structures are quite ramified in a network without large colloidal domains, cf. Fig. 2(e) and 5(a). This behavior would indicate that gels are, in a way, pictures of early critical fluids, where the cost of breaking bonds does prevent relaxation and thus the growth of the correlation length ξ .

Finally, in Fig. 5(f) we discuss the behavior of the bond distribution through its variance $\langle n^2 \rangle$. This has been shown recently for a similar colloid–polymer mixture model based on the Asakura–Oosawa potential that the variance of bond distribution as a function of V is peaked close to gelation.³⁸ We observe the same behavior in our simulations crossing the binodal, where $\langle n^2 \rangle$ exhibits a maximum for $V \simeq 3.5$. Upon quenching further the variance decreases, indicating a progressive aging of the network structure. The behavior of the variance will of course depend on time and other factors such as hydrodynamic interactions.^{33,65} In experiments, we also observe a growth of $\langle n^2 \rangle$ for equilibrium fluids ($V < 3$). We find larger

variances for gel samples, but not as high as in simulations, which is also confirmed by image shown for ξ in Fig. 5(e), where the gel structure corresponds to an arrested critical fluid. We return to the behaviour in the gel state in Section IVC.

D. Local structure

We now go to smaller scales and enquire what type of local structures emerge in a fluid close to criticality, and on their role in the dynamical arrest of the gel network. We have seen that in our experiments the typical length scale before gelation reaches $\approx 2\sigma$, emphasizing that the change in the dynamics at gelation is quite local and might only be caused by the first neighbor shell of each particle. To gain insights into the local structure of the super-critical fluid, we employ the topological cluster classification (TCC).⁵⁵ We use the same bond network as described in the Methods section. From the TCC, we extract the population of clusters of size m composed of 3–13 particles. This includes crystal structures like face-centered cubic (fcc) and hexagonal close-packed (hcp). In the TCC, each cluster type is labeled with two characters mX , with m is the number of particles composing the cluster and X is a letter to distinguish different spatial symmetries. Those letters follow the convention

of the minimum energies of various potentials such as the Morse potential.⁶⁶ We then identify for each cluster size m the predominant type X which corresponds to a minimum energy structure, a locally favored structure (LFS).¹⁶ In practice, we determine these clusters by following the global population spectrum of all clusters at different values of the attraction strength V . The population frequency of a cluster of type c is computed as N_c/N , with N_c the number of particles composing a cluster of type c and N the total number of particles. In the experimental data, we do not consider colloidal particles that are less than σ away from an edge.

In Fig. 6(a), we show the population of clusters comparing experiments and simulations. We find an excellent agreement, which demonstrates that mapping to the SW fluid also reproduces the higher-order structural features present in the experiments. We pick three different state points along the critical isochore including a hard-sphere fluid ($V = 0$), near-critical fluid ($V = 2.9$), and gel ($V = 3.2$). We first notice that the overall histograms show that when increasing V (from top to bottom), larger clusters composed of more than 10 particles appear. Additionally, we do not observe any signature of crystallization, *i.e.* no fcc nor hcp. However, we find that medium-sized clusters with $5 < m < 10$ grow progressively with respect to V , and always with the same order among clusters with equal number m of particles. In the following, we exclude larger clusters with $m > 12$ from the discussion since their weights are negligible.

IV. Discussion

A. Entropy favors low-symmetry clusters

For isolated clusters it has been shown that the relative population of clusters with the same number of bonds is determined

by entropy.^{15,67} Interestingly, this still holds for the fluid and even the gel as shown in Fig. 6(b) for $m = 6$. We find that 6Z clusters, which are polytetrahedra, are always significantly more prevalent in the system compared to 6A clusters, which are octahedra (the population goes up from $\approx 5\%$ for isolated 6A to $\approx 10\%$ in the fluid). The same trend can be observed for other clusters, with the more symmetric clusters being less populated. This demonstrates that the minimum (free) energy clusters are determined by rotational and vibrational entropies. It has also been shown that the potential part of the free energy will promote both octahedral and tetrahedral orders. The same observation was found in a more recent numerical study of the SW fluid,¹⁹ where gelation was associated with the polytetrahedral order. Another important observation is that we also find a large population of clusters with fivefold symmetry (8B, 9B, and 10B) at any V . These structures are known to be local energy minima of the Morse potential.⁶⁶ Hence, even though a gel is in an energy landscape far away from the equilibrium state, it can still locally minimize its free energy by forming isolated locally favored structures, which eventually will overlap and form the gel network. For larger clusters with 11 and 12 particles, we observe several Morse minima that correspond to $10 < \rho_0 < 25$ (ρ_0 is the Morse potential parameter controlling the range of attraction, in our case δ). The range for ρ_0 found here is consistent with short range attraction. We found that 11E and 12D are the dominant structures for $m = 11$ and $m = 12$ respectively, which corresponds to $\rho_0 \approx 17$.⁶⁶

B. Hard sphere fluid

Having obtained a set of minimum energy clusters, we use these clusters to follow the overall structural change in the

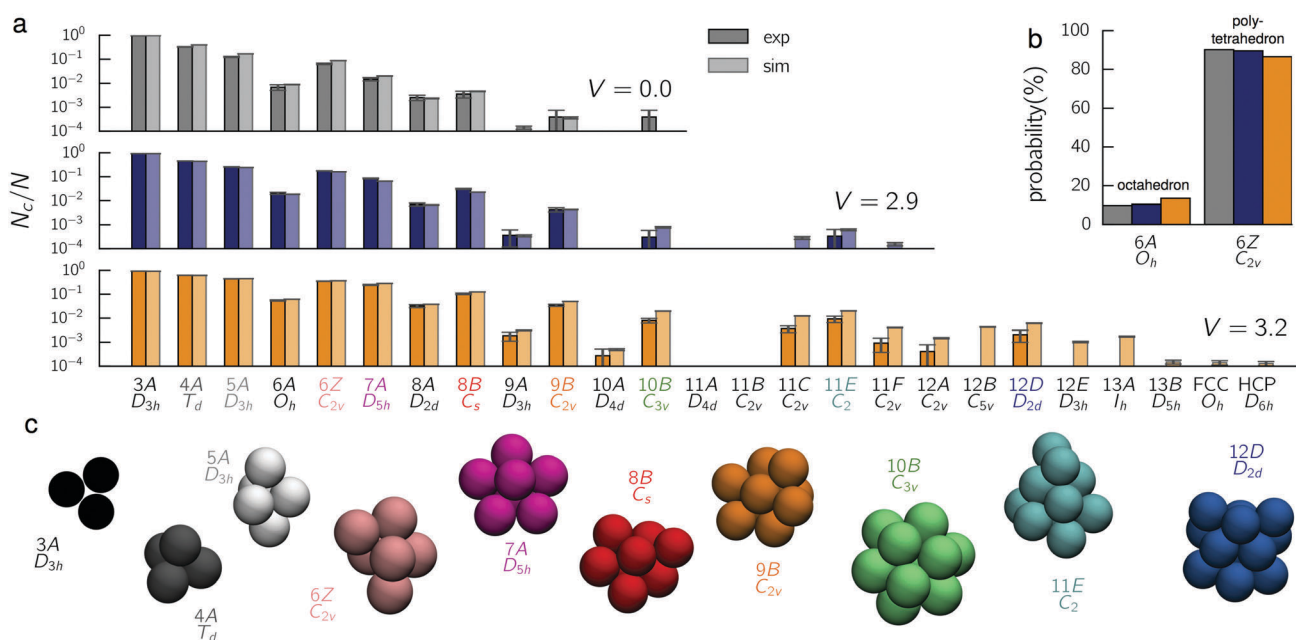


Fig. 6 Identification of locally favored structures. (a) Populations of local clusters for three different samples along the critical density, $\phi_c \approx 0.275$. From top to bottom: a hard-spheres sample, a critical fluid, and an arrested gel. (b) Experimental probability to observe octahedron and polytetrahedron in clusters composed of 6 particles. Colors distinguish the three different samples along the critical isochore. (c) Snapshots of selected locally favored structures.

fluid. As a reference, we first consider the compression of the hard sphere fluid ($V = 0$) towards the glass shown in Fig. 7(a). At low density, $\phi \simeq 0.05$, there is an absence of clusters as one can expect since particles are mostly isolated without any neighbors. At this low density, the system exhibits as a larger cluster with only a few percents of 4A (tetrahedron). The typical spatial arrangement of clusters is illustrated with an experimental snapshot in Fig. 8(a1). We then observe a rapid change from $\phi = 0.05$ to 0.25, where medium-sized clusters such as 5A, 6Z, 7C, and 8B start to appear, cf. Fig. 8(a1–a3). This continues until a crossover at $\phi > 0.25$, where isolated and small clusters (3A and 4A) are converted with a combination of medium clusters (5A, 6Z, 7C, and 8B) to larger structures: 9B, 10B, 11E, and 12D, see Fig. 8(a4). This kind of conversion will continue at higher packing fractions with the extinction of 5A, 6Z, and 7C to promote clusters sharing the same sub-structures. We also notice that the agreement between experiments and simulation is excellent. This gives another confirmation for the robustness of the mapping procedure employed.

C. En route to the gel

In Fig. 7(b), we follow the same idea but now approaching the gel. We fix the density to the critical packing fraction $\phi_c = 0.275$ and progressively increase the attraction strength V towards the binodal. We find a plateau with little change in structure until $V \simeq 2$. We show the spatial arrangement of clusters at $V = 1.1$ in Fig. 8(b1), where we only display clusters with $m > 4$. For higher attraction strengths, $V > 2$, we observe a structural crossover (cf. the compression of hard spheres). Clusters with $m > 4$ increase quickly until reaching the binodal. Interestingly, this change starts where we have located the beginning of

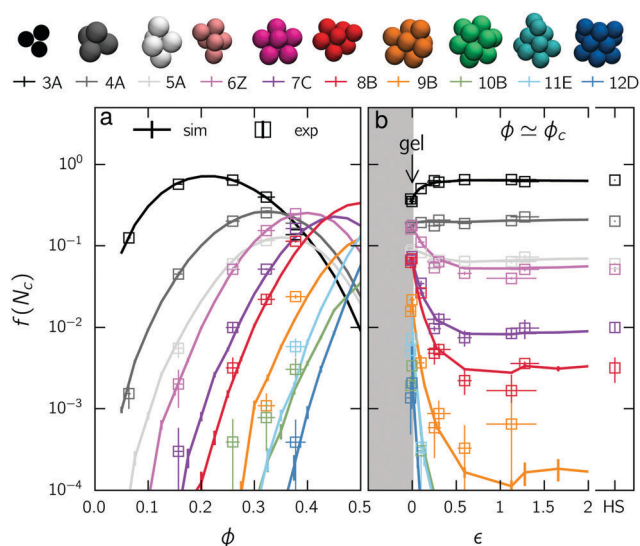


Fig. 7 Evolution of LFS through compression and cooling. (a) Evolution of the fraction of locally favored structures as a function of the packing fraction ϕ for hard spheres ($V = 0$). (b) Evolution of the fraction of locally favored structures as a function of the reduced attraction strength ϵ . The yellow area indicates the two-phase region where gelation occurs. Solid lines and open squares indicate the results for simulations and experiments, respectively.

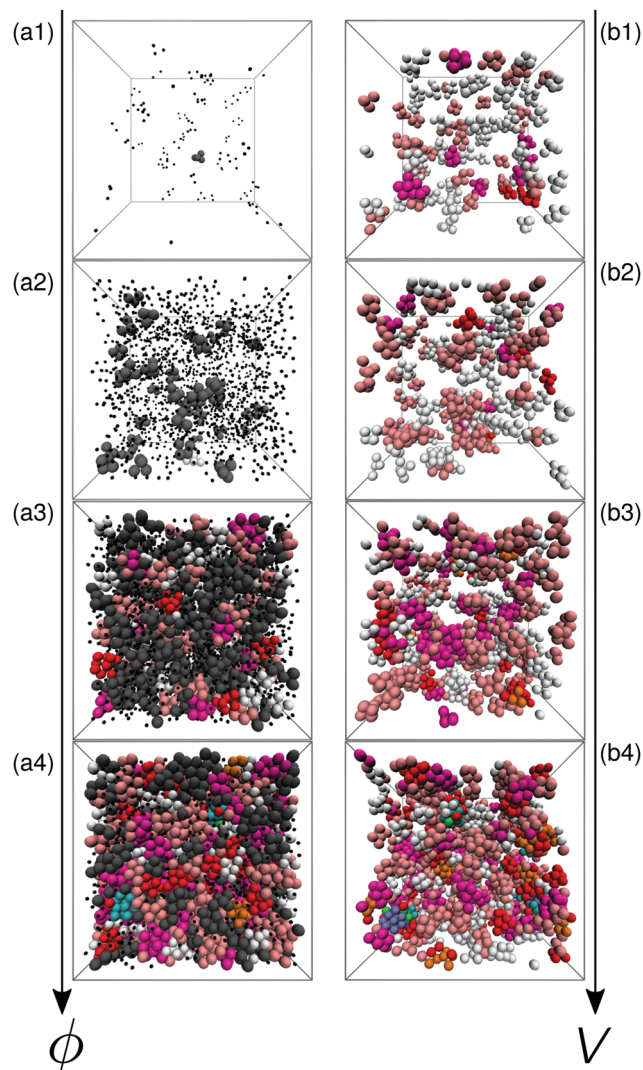


Fig. 8 Experimental snapshots of the cluster evolution. Evolution of the clusters when increasing the packing fraction ϕ (left) and attraction strength V (right). Only structures with $m > 4$ are shown for the cooling path.

critical scaling for the bulk correlation length ξ and the static susceptibility χ . The main contribution to this structural evolution comes from the creation of a large amount of 6Z, 7C, and 8B clusters, see Fig. 8(b1–b3). These clusters are not necessarily localized in space, but we do observe denser regions with even the presence of 9B at $V = 2.9$, see Fig. 8(b3). This is consistent with our previous findings in Fig. 4(c), where the density distribution exhibits a broader tail toward large packing fractions $\phi > 0.4$. Therefore, we can expect a link between the local structures of dense hard spheres and the colloidal-rich regions arising from critical density fluctuations. Finally at $V > V_c$, which corresponds to our first identification of a gel, clusters percolate the whole system, see Fig. 8(b4). The inner parts of the percolating structure are rich in large clusters such as 8B, 9B, and 10B, which are defective icosahedra sharing a fivefold symmetry. They are known to play an important role in the slowing down of the dynamics for dense hard-spheres

approaching the glass transition.^{18,68,69} This may help to explain the origin of the rigidity of the network leading to gelation.^{29,34}

The crucial difference between a gel and a dense hard sphere liquid is that not only the defective icosahedra (8B, 9B, and 10B) are very stable due to entropy, but each bond breaking will also result in an energetic penalty of more than $3k_B T$. Therefore only colloids in the outer part of dense regions will be able to break bonds and diffuse (see the ESI,† Video). To conclude, we find that the structural crossover starts $1k_B T$ before the location of the binodal when increasing V . This is a direct consequence of criticality inducing larger density fluctuations. For a monodisperse sample, these fluctuations might promote crystal precursors and lower the nucleation time.¹⁹ For a polydisperse sample, however, they induce low-symmetry polytetrahedral backbones for the bond network. These clusters are incompatible with respect to the crystal symmetry. Hence, the system will fall into an amorphous solid state, the gel.

V. Conclusions

We have investigated the role of criticality in the gelation of sticky spheres. Combining experiment and simulations, we provide further evidence that the dynamical arrest is initiated by the onset of critical fluctuations in agreement with previous work.^{8,16,29,34} We have demonstrated that carefully mapping two-point structure to the square-well fluid faithfully reproduces the experimental data including higher-order local structures as identified by the topological cluster classification method.⁵⁵ In particular, we find that gel samples are (i) located at the cumulant crossing, (ii) identified by a broad distribution of densities, and (iii) have correlation lengths of $\xi \simeq 2\sigma$. We find a sharp but continuous increase of locally favored structures when increasing the attraction strength. This increase occurs in concert with the increase of both the bulk correlation length and the static susceptibility, which can be extracted together with the structure factor of the fluid. More precisely, the start of the critical scaling of these two quantities coincides with the appearance of larger locally favored structures. The picture of a gel is thus that of an early critical fluid, which is arrested due to the large cost of breaking bonds. Before arrest, clusters of several particles appear, which have a low symmetry favored by entropy. The densification of these clusters driven by the incipient critical fluctuations then leads to the gel.

Conflicts of interest

There are no conflicts of interest to declare.

Appendix A: effective colloid diameter

There are two challenges for the determination of the effective packing fraction and the effective temperature of a colloidal sample from real space imaging. First, it is difficult to know the

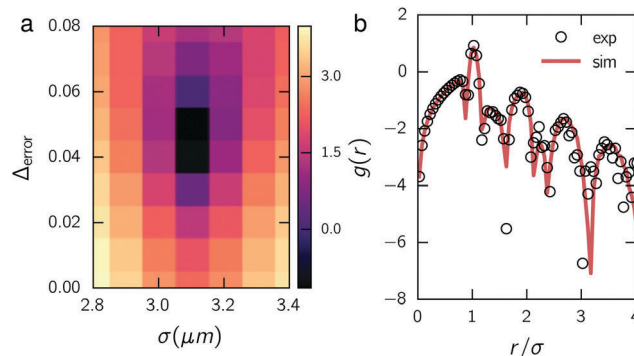


Fig. 9 Effective diameter and tracking errors. (a) Color map of $\ln(\chi^2)$ against the effective diameter σ and the tracking error Δ_{error} . (b) Resultant matching of the pair correlation between an experimental sample and simulation at criticality ($\phi = 0.275$, $V = 3.2$).

change in the colloidal diameter in solution due to swelling and unscreened electrostatics.^{50,51} This leads to a poor estimation of the sample packing fraction and, e.g., a mismatch of structural oscillations in pair correlations. Second, errors due to imaging and tracking will lead to an error on the true position of a particle, resulting in a broadening of the peaks of a pair correlation.⁴⁶ In the context of matching a sample's $g(r)$ onto simulations, these errors will induce a systematic overestimation of the temperature of a mixture at a given polymer concentration c_p . To handle these issues, we pick a sample close to criticality and compute its pair correlation $[g(r) - 1]$ for various effective diameters. To mimic tracking errors, we pick a simulation state point at criticality and apply different Gaussian noises of variance Δ_{error} to the particle positions. We then find the optimal set of parameters that minimize $\chi^2 = \sum_i [r_i(h_{\text{exp}}(r_i) - h_{\text{sim}}(r_i))]^2$.

The evolution of χ^2 as a function of the parameters is shown in Fig. 9(a). We find a unique minimum for χ^2 leading to an effective diameter $\sigma = 3100$ nm (5% larger than for dry colloids) and a tracking error $\Delta_{\text{error}} = 5\%$, which is consistent with previous studies.⁴⁶ The resulting matched pair correlation function is shown in Fig. 9(b). We observe a very good agreement between experiment and simulation which validate σ and Δ_{error} .

Acknowledgements

We gratefully acknowledge F. Turci and M. Campo for stimulating discussions. We thank M. Schmiedeberg for helpful comments. We acknowledge financial support by the DFG through the collaborative research center TRR 146 (D.R.).

References

- 1 P. G. Debenedetti and F. H. Stillinger, *Nature*, 2001, **410**, 259.
- 2 L. Berthier and G. Biroli, *Rev. Mod. Phys.*, 2011, **83**, 587.
- 3 G. Biroli and J. P. Garrahan, *J. Chem. Phys.*, 2013, **138**, 12A301.
- 4 L. Berthier and M. D. Ediger, *Phys. Today*, 2016, **69**, 40.

- 5 F. Turci, C. P. Royall and T. Speck, *Phys. Rev. X*, 2017, **7**, 031028.
- 6 C. P. Royall and S. R. Williams, *Phys. Rep.*, 2015, **560**, 1.
- 7 C. P. Royall, F. Turci, S. Tatsumi, J. Russo and J. F. E. Robinson, 2017, ArXiv p. 1711.04739.
- 8 S. Manley, H. Wyss, K. Miyazaki, J. Conrad, V. Trappe, L. Kaufman, D. Reichman and D. Weitz, *Phys. Rev. Lett.*, 2005, **95**, 238302.
- 9 S. Griffiths, F. Turci and C. P. Royall, *J. Chem. Phys.*, 2017, **146**, 014905.
- 10 W. Poon, *J. Phys.: Condens. Matter*, 2002, **14**, R859.
- 11 W. Van Megen and P. Pusey, *Phys. Rev. A: At., Mol., Opt. Phys.*, 1991, **43**, 5429.
- 12 E. De Hoog, W. Kegel, A. Van Blaaderen and H. Lekkerkerker, *Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys.*, 2001, **64**, 021407.
- 13 L. Cipelletti and L. Ramos, *J. Phys.: Condens. Matter*, 2005, **17**, R253–R285.
- 14 E. Zaccarelli, *J. Phys.: Condens. Matter*, 2007, **19**, 323101.
- 15 G. Meng, N. Arkus, M. P. Brenner and V. N. Manoharan, *Science*, 2010, **327**, 560.
- 16 C. P. Royall, S. R. Williams, T. Ohtsuka and H. Tanaka, *Nat. Mater.*, 2008, **7**, 556.
- 17 S. L. Taylor, R. Evans and C. P. Royall, *J. Phys.: Condens. Matter*, 2012, **24**, 464128.
- 18 R. Pinchaipat, M. Campo, F. Turci, J. Hallet, T. Speck and C. P. Royall, *Phys. Rev. Lett.*, 2017, **119**, 028004.
- 19 T. K. Haxton, L. O. Hedges and S. Whitelam, *Soft Matter*, 2015, **11**, 9307.
- 20 J. Largo, M. Miller and F. Sciortino, *J. Chem. Phys.*, 2008, **128**, 134513.
- 21 M. G. Noro and D. Frenkel, *J. Chem. Phys.*, 2000, **113**, 2941.
- 22 A. Stradner, H. Sedgwick, F. Cardinaux, W. C. Poon, S. U. Egelhaaf and P. Schurtenberger, *Nature*, 2004, **432**, 492.
- 23 P. Katsonis, S. Brandon and P. G. Vekilov, *J. Phys. Chem. B*, 2006, **110**, 17638.
- 24 F. Platten, N. E. Valadez-Pérez, R. Castañeda-Priego and S. U. Egelhaaf, *J. Chem. Phys.*, 2015, **142**, 05B602_1.
- 25 M. Grant and W. Russel, *Phys. Rev. E: Stat. Phys., Plasmas, Fluids, Relat. Interdiscip. Top.*, 1993, **47**, 2606.
- 26 H. Verduin and J. K. Dhont, *J. Colloid Interface Sci.*, 1995, **172**, 425.
- 27 W. C. K. Poon, *J. Phys.: Condens. Matter*, 2002, **14**, R859.
- 28 E. Zaccarelli, *J. Phys.: Condens. Matter*, 2007, **19**, 323101.
- 29 P. J. Lu, E. Zaccarelli, F. Ciulla, A. B. Schofield, F. Sciortino and D. A. Weitz, *Nature*, 2008, **453**, 499.
- 30 M. Laurati, G. Petekidis, N. Koumakis, F. Cardinaux, A. B. Schofield, J. M. Brader, M. Fuchs and S. U. Egelhaaf, *J. Chem. Phys.*, 2009, **130**, 134907.
- 31 A. P. Eberle, N. J. Wagner and R. Castañeda-Priego, *Phys. Rev. Lett.*, 2011, **106**, 105704.
- 32 R. Pandey and J. C. Conrad, *Soft Matter*, 2013, **9**, 10617.
- 33 C. P. Royall, J. Eggers, A. Furukawa and H. Tanaka, *Phys. Rev. Lett.*, 2015, **114**, 258302.
- 34 C. P. Royall, S. R. Williams and H. Tanaka, *J. Chem. Phys.*, 2018, **148**, 044501.
- 35 J. Bibette, T. Mason, H. Gang and D. Weitz, *Phys. Rev. Lett.*, 1992, **69**, 981.
- 36 K. Kroy, M. Cates and W. Poon, *Phys. Rev. Lett.*, 2004, **92**, 148302.
- 37 N. E. Valadez-Pérez, Y. Liu, A. P. Eberle, N. J. Wagner and R. Castañeda-Priego, *Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys.*, 2013, **88**, 060302.
- 38 M. Kohl, R. Capellmann, M. Laurati, S. Egelhaaf and M. Schmiedeberg, *Nat. Commun.*, 2016, **7**, 11817.
- 39 N. A. M. Verhaegh, D. Asnaghi, H. N. W. Lekkerkerker, M. Giglio and L. Cipelletti, *Physica A*, 1997, **242**, 104.
- 40 K. N. Pham, A. M. Puertas, J. Bergenholtz, S. U. Egelhaaf, A. Moussad, P. N. Pusey, A. B. Schofield, M. E. Cates, M. Fuchs and W. C. Poon, *Science*, 2002, **296**, 104.
- 41 R. Baxter, *J. Chem. Phys.*, 1968, **49**, 2770.
- 42 S. Buzzaccaro, R. Rusconi and R. Piazza, *Phys. Rev. Lett.*, 2007, **99**, 098301.
- 43 H. He and M. Thorpe, *Phys. Rev. Lett.*, 1985, **54**, 2107.
- 44 H. Hinrichsen, *Adv. Phys.*, 2000, **49**, 815.
- 45 I. Bodnár, J. K. G. Dhont and H. N. W. Lekkerkerker, *J. Phys. Chem.*, 1996, **100**, 19614.
- 46 C. P. Royall, A. A. Louis and H. Tanaka, *J. Chem. Phys.*, 2007, **127**, 044507.
- 47 H. N. W. Lekkerkerker, W. C. K. Poon, P. N. Pusey, A. Stroobants and P. B. Warren, *Europhys. Lett.*, 1992, **20**, 559.
- 48 I. Zhang, C. P. Royall, M. A. Faers and P. Bartlett, *Soft Matter*, 2013, **9**, 2076.
- 49 M. Leocmach and H. Tanaka, *Soft Matter*, 2013, **9**, 1447.
- 50 W. C. Poon, E. R. Weeks and C. P. Royall, *Soft Matter*, 2012, **8**, 21.
- 51 C. P. Royall, W. C. Poon and E. R. Weeks, *Soft Matter*, 2013, **9**, 17.
- 52 F. Turci and C. P. Royall, *J. Stat. Mech.: Theory Exp.*, 2016, 084004.
- 53 A. S. Clarke and J. D. Wiley, *Phys. Rev. B: Condens. Matter Mater. Phys.*, 1987, **35**, 7350.
- 54 W. Brostow, J.-P. Dussault and B. L. Fox, *J. Comput. Phys.*, 1978, **29**, 81.
- 55 A. Malins, S. R. Williams, J. Eggers and C. P. Royall, *J. Chem. Phys.*, 2013, **139**, 234506.
- 56 K. Binder, *Z. Phys. B: Condens. Matter*, 1981, **43**, 119.
- 57 H. Watanabe, N. Ito and C.-K. Hu, *J. Chem. Phys.*, 2012, **136**, 204102.
- 58 M. Rovere, P. Nielaba and K. Binder, *Z. Phys. B: Condens. Matter*, 1993, **90**, 215.
- 59 S. Sengupta, P. Nielaba, M. Rao and K. Binder, *Phys. Rev. E: Stat. Phys., Plasmas, Fluids, Relat. Interdiscip. Top.*, 2000, **61**, 1072.
- 60 O. Galkin and P. G. Vekilov, *Proc. Natl. Acad. Sci. U. S. A.*, 2000, **97**, 6277.
- 61 A. Fortini, E. Sanz and M. Dijkstra, *Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys.*, 2008, **78**, 041402.
- 62 J. R. Savage and A. D. Dinsmore, *Phys. Rev. Lett.*, 2009, **102**, 198302.
- 63 T. Ohtsuka, C. P. Royall and H. Tanaka, *Europhys. Lett.*, 2008, **84**, 46002.

- 64 R. Rice, R. Roth and C. P. Royall, *Soft Matter*, 2012, **8**, 1163.
- 65 Z. Varga and J. Swan, *Soft Matter*, 2016, **12**, 7670.
- 66 J. P. Doye, D. J. Wales and R. S. Berry, *J. Chem. Phys.*, 1995, **103**, 4234.
- 67 A. Malins, S. R. Williams, J. Eggers, H. Tanaka and C. P. Royall, *J. Phys.: Condens. Matter*, 2009, **21**, 425103.
- 68 N. C. Karayiannis, R. Malshe, J. J. de Pablo and M. Laso, *Phys. Rev. E: Stat., Nonlinear, Soft Matter Phys.*, 2011, **83**, 061505.
- 69 J. Taffs, S. R. Williams, H. Tanaka and C. P. Royall, *Soft Matter*, 2013, **9**, 297.
- 70 C. P. Royall, J. Eggers, A. Furukawa and H. Tanaka, *Phys. Rev. Lett.*, 2015, **114**, 258302.